

# Changes in wood tree species *Fagus sylvatica* L. and characteristics of the thermal process of modifying its color with saturated water steam

Ladislav Dzurenda, Michal Dudiak

*Faculty of Wood Sciences and Technology, Technical University in Zvolen, 960 53 Zvolen, Slovakia.*

Received: January 15, 2020 / Accepted: February 22, 2020 / Published: Vol. 5, Issue 04, pp. 142-156, 2020

**Abstract:** The aim of this work is to present changes in beech wood acquired in the targeted process of color modification of sapwood and mature beech wood with saturated water steam with temperatures  $t_I = 105 \pm 2.5$  °C for  $\tau = 6$  hours. (Mode I),  $t_{II} = 127.5 \pm 2.5$  °C for  $\tau = 6.5$  hours (Mode II),  $t_{III} = 137.5 \pm 2.5$  °C for  $\tau = 7$  hours (Mode III), and also to present characteristics of the technological process in terms of heat and saturated steam consumption.

On the basis of experimental work and subsequent analyzes, for individual modes of thermal modification of beech wood color by water steam, the following are determined:

- the density of thermally treated beech wood with saturated steam,
- the acidity of thermally treated beech wood with saturated steam,
- coordinates of lightness  $L^*$ , red color  $a^*$  and yellow color  $b^*$  of thermally treated beech wood in CIE  $L^* a^* b^*$  color space,
- heat consumption per 1 m<sup>3</sup> of thermal modification of beech wood color with water steam,
- consumption of saturated water steam per 1 m<sup>3</sup> of thermal modification of beech wood color with saturated water steam.

**Keywords:** beech wood, the CIE- $L^* a^* b^*$  colour space, thermal treatment, saturated water steam, technical and technological parameters.

## 1. Introduction

The color of the wood is one of the macroscopic features that distinguishes the wood of individual woods visually from each other. The color of the wood is created by chromophores, it means functional groups of the type:  $>C=O$ ,  $-CH=CH-CH=CH-$ ,  $-CH=CH-$ , aromatic cores, that absorb the light in the region of UV-VIS radiation, located in chemical components of wood (lignin and extractive substances such as dyes, tannins, resins and others).

---

**Corresponding author:** Ladislav Dzurenda, Faculty of Wood Sciences and Technology, Technical University in Zvolen, 960 53 Zvolen, Slovakia, mail: dzurenda@tuzvo.sk

Wood placed in the environment of hot water, saturated water steam or saturated humid air is heated and changes its physical, mechanical and chemical characteristics.

Wood thermal treatment processes, in addition to targeted physico-mechanical changes used in the production of veneers, plywood, bent furniture or pressed wood, are also accompanied by chemical wood changes and color changes (Kollmann and Gote 1968; Nikolov *et al.* 1980; Sergovskij and Rasev 1987; Trebula 1986; Lawnniczak 1995; Dzurenda and Orłowski 2011; Dzurenda 2013). In the past, the color changes of wood darkening in the technological steaming process have been used to eliminate unwanted color differences between light sapwood and dark hardwood or to remove unwanted color spots caused by evaporation, browning or molding. In recent years the research has focused on targeted color changes of individual tree species to more or less distinct color shades, respectively wood imitations of domestic trees for exotic woody plants (Molnar 2002; Tolvaj *et al.* 2010; Dzurenda 2014, 2018a, b; Barcik *et al.* 2015; Baranski *et al.* 2017).

Beech belongs to the scattered-porous wood. Beech wood is medium heavy, flexible, easily cleavable. It has good mechanical properties, it is bendable and very well to plasticized and mechanical treat. Due to the high permeability, it is well for impregnation, pickling and coloring. Dry beech wood of sapwood and mature wood without hardwood is light white-gray with a yellow shade. The color of hardwood is dark brown-red. Beech wood is used for the production of furniture, floors, sports equipment, toys and small household items.

The aim of this work is to determine the properties of beech wood, such as density, acidity, color acquired by the thermal treatment process - modification of beech wood color by saturated water vapor in modes with temperatures  $t_I = 105 \pm 2.5$  °C for  $\tau = 6$  hours. (Mode I),  $t_{II} = 127.5 \pm 2.5$  °C for  $\tau = 6.5$  hours (Mode II),  $t_{III} = 137.5 \pm 2.5$  °C for  $\tau = 7$  hours (Mode III), and also to determine the characteristics of the technological process in terms of heat and saturated steam consumption.

## 2. Methodology

### Materials

The timber tree species *Fagus sylvatica* L. in the form of lumber with thickness  $h = 40$  mm with moisture content above the saturation point of fibers was thermally modified with saturated steam in the pressure autoclave: APDZ 240 (Himmasch AD, Haskovo, Bulgaria) at Sundermann s.r.o. Banská Štiavnica.

### Methods

The density of dry wood was determined according the standard STN 49 0108: 1993 Wood - Density determination. Density was calculated from the measured sample weights and volumes using the equation:

$$\rho_0 = \frac{m_0}{V_0} \quad [\text{kg} \cdot \text{m}^{-3}] \quad (1)$$

Where:  $m_0$  – is weight of dry sample [kg],

$V_0$  – is volume of dry sample [ $\text{m}^3$ ].

The conditions of thermal treatment for modification the color of beech wood by saturated water steam are shown in Figure 1. Schedule of saturated water steam temperatures for each color modification stage (mode) is specified in Table 1.

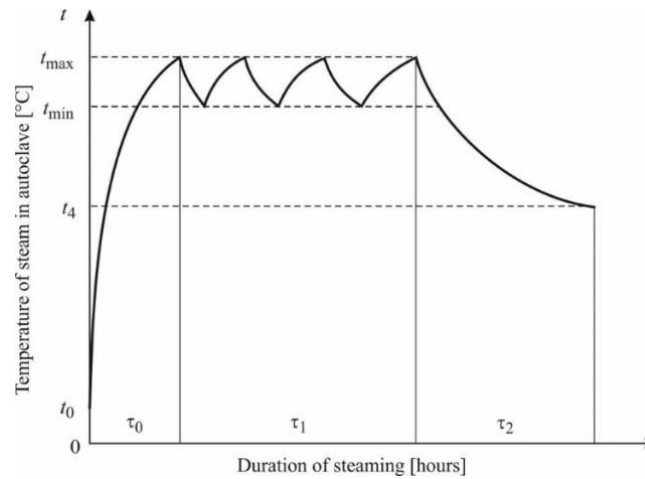


Fig. 1. Mode of color modification of beech wood with saturated water steam

Table 1 Modes of thermal treatment of beech wood with saturated steam

Modes	Temperature of saturated steam [°C]			Steaming time in hours [hours]			
	$t_{\max}$	$t_{\min}$	$t_4$	$\tau_0$ - heating	$\tau_1$ - phase I	$\tau_2$ - phase II	Total time
Steaming mode I.	107.5	102.5	100	$\approx 1.5$	3.5	1.0	$\approx 6.0$
Steaming mode II.	130.0	125.0	100		4.0	1.0	$\approx 6.5$
Steaming mode III.	140.0	135.0	100		4.5	1.0	$\approx 7.0$

It was measured the moisture content and acidity of wet beech wood on the set of 35 timber samples before the thermal process and after the thermal treatment of timber by each mode after its completion and after cooling of the wood to ambient temperature.

The moisture content of wet beech wood above the fiber saturation point was measured with the resistance humidity meter of type: FMD6.

The measurement of acidity of wet wood was performed with meter SENTRON SI 600 and probe LanceFET+H. The pH probe has a diameter of  $d = 10$  mm and cannot be immersed in a solid material. Because of that reason, the 12 mm hole was created with cordless drill at the measurement point. The drilling sawdust were poured into the formed hole and the probe LanceFET+H of meter SENTRON SI 600 was inserted in to the wet sawdust (Geffert *et al.* 2019).

Subsequently, the thermally modified and unmodified beech timber was dried to a moisture content  $W_p = 12 \pm 0.5\%$  in a conventional hot air dryer: KAD 1x6 (KATRES s.r.o). By means of longitudinal and transverse manipulation, wood blanks with dimensions: 27 x 75 x 600 mm were made. All surfaces of blanks were machined on the horizontal plane milling machine FS 200.

The color measurement of both untreated and thermally treated beech wood with a moisture content  $W_k = 12 \pm 0.5\%$  was performed on all surfaces at a distance of 300 mm from the front of the blank. The color of the beech wood blanks in the CIE- $L^* a^* b^*$  color space was measured with a colorimeter Color Reader CR-10 (Konica Minolta, Japan). There was used light source D65 and the diameter of the optical scanning hole was 8 mm. In the CIE  $L^* a^* b^*$  and CIE  $L^* C^* h^\circ$  color spaces, the color was considered based on changes in the luminance coordinate  $L^*$ , the chromatic coordinate of the red color  $a^*$ , the chromatic coordinate of the yellow color  $b^*$  and the chroma  $C^*$ . Chroma  $C^*$  is the integrated value of the red  $a^*$  and yellow  $b^*$  coordinates on the chromatic plane of the cylindrical color space CIE  $L^* C^* h^\circ$ .

$$C^* = \sqrt{a^{*2} + b^{*2}} \quad (2)$$

Where:  $a^*$  - value on chromatic coordinate of red color,  
 $b^*$  - value on chromatic coordinate of yellow color.

From the difference of the values on the color coordinates  $\Delta L^*$ ,  $\Delta a^*$ ,  $\Delta b^*$  that were determined on the basis of measurements both thermal treated and untreated beech wood surface, the total color difference  $\Delta E$  was determined according to the following equation *ISO 11 664-4*:

$$\Delta E^* = \sqrt{(L_2^* - L_1^*)^2 + (a_2^* - a_1^*)^2 + (b_2^* - b_1^*)^2} \quad (3)$$

Where:  $L_1^*$ ,  $a_1^*$ ,  $b_1^*$  - values on the color space coordinates of the surface of dried milled thermally untreated beechwood,  
 $L_2^*$ ,  $a_2^*$ ,  $b_2^*$  - values on the color space coordinates of the surface of dried milled thermally treated beechwood.

The change of color in wood, except of changes on chromatic coordinates in the CIE  $L^* a^* b^*$  color space, was also assessed by changes in lightness  $\Delta L^*$ , changes in chroma  $\Delta C^*$  and hue angle  $h^\circ$  in cylindrical color space CIE  $L^* C^* h^\circ$ .

Hue angle  $h^\circ$  defines the deviation of chroma  $C^*$  from the coordinate of red color in the chromatic plane that describe the equation:


$$h_{ab}^\circ = \arctan\left(\frac{b^*}{a^*}\right) \quad (4)$$

Where:  $a^*$  - value on chromatic coordinate of red color,  
 $b^*$  - value on chromatic coordinate of yellow color.

The consumption of saturated water steam for the realization of the technological process for 1 m<sup>3</sup> of wood was determined by model of heat consumption per 1 m<sup>3</sup> for the thermal treatment of wood in the pressure autoclave APDZ 240 Dzurenda (2016):

$$Q_{ha} = \frac{Q_{hw} + Q_{hf} + Q_{hil} + Q_{he} + Q_{hfv} + Q_{hew}}{V_w} \quad [\text{MJ/m}^3] \quad (5)$$

Where:  $Q_{hf}$  – heat necessary to heat the construction material of the autoclave, MJ;

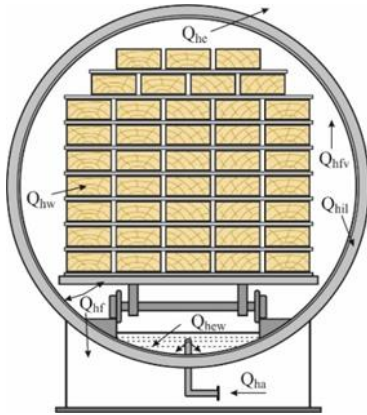

$Q_{hw}$  – heat necessary for heating colour modification wood, MJ;

$Q_{hil}$  – heat necessary to heat the autoclave's insulation, MJ;

$Q_{he}$  – at necessary to cover heat losses from the surface of the pressure autoclave, MJ;

$Q_{hfv}$  – heat extracted by condensate from the pressure autoclave, MJ;

$Q_{hew}$  – heat extracted by saturated steam after opening the autoclave, MJ;

$V_w$  – volume of the colour modification wood in the pressure autoclave, m<sup>3</sup>.

Figure 2. The heat distribution in the autoclave in the process of modifying the color of the wood with saturated water steam.

The consumption of saturated water steam for color modification of 1 m<sup>3</sup> of beech wood is evaluated by the equation:

$$m'' = \frac{Q_{ha}}{h'' - h'} \quad (6)$$

Where:  $Q_{ha}$  – heat consumption standard for modification of 1 m<sup>3</sup> of beech timber, MJ / m<sup>3</sup>;

$h''$  – enthalpy of saturated water steam at temperature  $t_{max}$ , kJ/kg;

$h'$  – enthalpy of saturated water at temperature  $t_4$ , kJ/kg.

### 3. Results and Discussion

The physical properties of wood *Fagus sylvatica* L such as: wood moisture content and acidity of wet wood before the thermal treatment process as well as wood density, color space coordinates CIE L\* a\* b\* and chroma C\* in the dry state, are shown in Table 2.

Table 2 Measured values of density, color space coordinates of CIE L\* a\* b\* of dry wood, moisture content and acidity of wet beech wood

Timber	Dry beech wood					Wet beech wood	
	Wood density	Color space coordinates CIE L*a*b*				Moisture content	Acidity
	$\rho_0$ [kg·m <sup>-3</sup> ]	L*	a*	b*	C*	W [%]	pH
Beech	683.5 ± 65.1	76.6 ± 2.3	6.8 ± 1.8	19.8 ± 1.7	20.9	56.4 ± 3.3	5.2 ± 0.1

The measured density values of beechwood in the dry state are the average values of healthy density, fungi

or molds of undamaged beech sapwood. Similar values of beech wood density for Central European territory are mentioned in the works: (Požgaj *et al.* 1997; Makoviny 2010; Kurjatko *et al.* 2010). On the basis of this statement, the analyzed changes of characteristics in beech wood achieved by thermal treatment in individual modes can be marked as representative (standard).

Table 3. shows the results of laboratory work determining the density of both untreated and treated beechwood by the individual modes in the dry state.

Table 3 Densities of dry, untreated and treated beech wood

Thermal modification modes	Statistical characteristics of wood density in the dry state			
	$\rho_0$ [kg·m <sup>-3</sup> ]	s [kg·m <sup>-3</sup> ]	$v_x$ [%]	n [-]
Untreated wood	683.5	65.1	9.5	18
Modification mode I.	671.8	58.5	8.7	16
Modification mode II.	691.9	60.1	8.7	18
Modification mode III.	705.0	67.8	9.6	17

The variations in density of dry beech wood due to the thermal treatment of the individual modes are contradictory. The density of dry thermally modified beechwood by mode I is less about  $\Delta\rho_0 = - 1.74$  % and by the mode II. and III. grows up. The density of dry beech wood treated by mode II. about  $\Delta\rho_0 = + 1.21$  % and by mode III. about  $\Delta\rho_0 = + 3.05$  %. From the presented results follows, that due to the hydrolysis of the polysaccharide fraction of beechwood and due to the extraction of water-soluble substances by the thermal treatment processes of individual modes, the density of beechwood changes partially. The changes in the densities of the color-modified beech wood do not exceed the limits of natural density tolerance of beech wood, which are in the Central European area:  $\rho_0 = 490\text{--}680\text{--}880$  kg·m<sup>-3</sup>.

The acidity of wet wood of most tree species from the temperate zone is in the range of pH = 3.3 – 6.4 (Sandermann and Rothkamm 1956; Irle 2012; Solar 2014; Geffert *et al.* 2019). The acid reaction of most wood tree is caused by free acids and acid groups that are in aqueous solutions of dilute sugars, organic acids and water-soluble inorganic substances fed to the tree in the lumen of cells by the root system (Čudinov 1968; Blažej *et al.* 1975; Zevenhoven 2001, Pňakovič and Dzurenda). The measured acidity values of wet thermally untreated beech wood are pH =  $5.2 \pm 0.2$  at moisture content  $w \approx 56.4$  % and do not differ from the acid values of beech wood with moisture content above the point of saturated fibers reported by the authors: (Solar 2004; Geffert *et al.* 2019 ). The acidity values of wet thermally modified beech wood by individual modes after cooling to ambient temperature are shown in Table 4.

Table 4 Measured moisture content and acidity values of thermally modified beech wood

Mode	Temperature of saturated water steam	Wood moisture content	pH value
Modification mode I.	$t_I = 110 - 115$ °C	$w \approx 48.7$ %	pH = $4.5 \pm 0.2$
Modification mode II.	$t_{II} = 125 - 130$ °C	$w \approx 45.3$ %	pH = $4.0 \pm 0.3$
Modification mode III.	$t_{III} = 135 - 140$ °C	$w \approx 44.5$ %	pH = $3.7 \pm 0.3$

The decrease in the pH of thermally modified beech wood by the individual color modification modes confirms the known knowledge about the process of hydrolysis mainly hemicelluloses in the wet wood of leafy tree under the influence of heat, as reported by: (Melcer *et al.* 1989; Laurova *et al.* Samešova *et al.* 2018; Geffert *et al.* 2019; Dzurenda and Dudiak 2019).

Depending on the temperature and duration of action of the hydrolysis products: acetic acid and formic acid, degradation occur of polysaccharides by carbohydrate and pectin oxidation, dehydration of pentose to 2-furaldehyde and in lignin begin to form free radicals and phenolic hydroxyl groups, resulting in the formation of new chromophoric groups causing wood color change (Fengel and Wegener 1989; Solár 2004; Bučko 2005). These reactions results in the formation of new chromophoric groups that cause color changes in the wood. This is illustrated by the visual change in color of beech wood in Figure 3. and the of changes in the CIE L\* a\* b\* color space of the thermally modified beech wood in Table 5.

The color of the dried, planed, steam untreated beech wood and the color shades obtained by the heat treatment modes – with saturated water steam are shown in Figure 3.

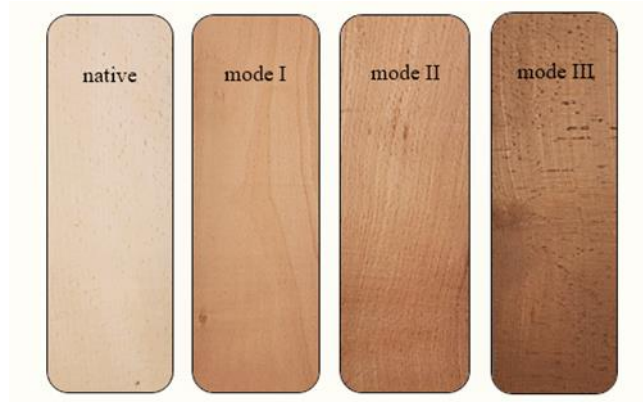


Fig. 3. View of beech wood before and after heat treatment by individual modes.

The coordinate values describing the color of beech wood before and after thermal treatment by each mode in CIE L\* a\* b\*, chroma C\* and total color difference  $\Delta E^*$  are shown in Table 5.

Table 5 CIE L\* a\* b\* color space coordinate values describing beech wood before and after saturated water steam treatment with each steam mode

Temperature of saturated water steam	CIE-L* a* b* color space coordinates			Chroma	Total color difference
	L*	a*	b*	C*	$\Delta E^*$
Not thermally treated wood	$76.6 \pm 2.3$	$6.9 \pm 1.8$	$19.8 \pm 1.7$	20.9	- - -
$t_I = 110 - 115 \text{ }^\circ\text{C}$	$71.5 \pm 2.1$	$11.1 \pm 1.7$	$21.5 \pm 1.5$	24.2	6.8
$t_{II} = 125 - 130 \text{ }^\circ\text{C}$	$63.2 \pm 2.4$	$14.9 \pm 2.1$	$23.3 \pm 1.7$	27.6	16
$t_{III} = 135 - 140 \text{ }^\circ\text{C}$	$54.3 \pm 2.4$	$15.6 \pm 1.9$	$24.1 \pm 1.6$	28.7	24.4

The color of dry, untreated beech wood identified by coordinates  $L^* = 76.6 \pm 2.3$ ;  $a^* = 6.9 \pm 1.8$ ;  $b^* =$

$19.8 \pm 1.7$  color space CIE  $L^* a^* b^*$  is comparable to the color coordinate values reported for beech wood by: (Babiak *et al.* 2004; Dzurenda 2014; Meints *et al.* 2017).

The thermally treated beech wood at temperature of saturated water steam  $t_I = 105 \pm 2.5^\circ\text{C}$  for  $\tau = 6$  hours acquire a pale brown-pink-yellow shade. In the CIE color space  $L^* a^* b^*$  it is identified by the coordinate values:  $L_I^* = 71.5 \pm 2.1$ ;  $a_I^* = 11.1 \pm 1.7$ ;  $b_I^* = 21.5 \pm 1.5$ . The total color difference  $\Delta E_I^* = 6.8$  according to the colorimetric classification of wood color changes during thermal treatment processes of wood processing (Cividini *et al.* 2007) classifies achieved color change into the changes perceptible to the naked eye. The significant color changes of beech wood by thermal treatment are achieved by modes II. and III with a saturated water steam temperature of  $t_{II} = 127.5 \pm 2.5^\circ\text{C}$ , respectively by temperature  $t_{III} = 137.5 \pm 2.5^\circ\text{C}$ . Thermal treatment of mode II. by the temperature  $t_{II} = 127.5 \pm 2.5^\circ\text{C}$  for  $\tau = 7.5$  hours the beech wood acquires a brown-pink color with the coordinates:  $L_{II}^* = 63.2 \pm 2.4$ ;  $a_{II}^* = 14.9 \pm 2.1$ ;  $b_{II}^* = 23.3 \pm 1.7$ . Original brown-red color with color coordinate values:  $L_{III}^* = 54.3 \pm 2.4$ ;  $a_{III}^* = 15.6 \pm 1.9$ ;  $b_{III}^* = 24.1 \pm 1.6$  the beech wood acquires by thermal treatment conditions at a saturated steam temperature  $t_{III} = 137.5 \pm 2.5^\circ\text{C}$ . The total color difference  $\Delta E_{III}^* = 24.4$  achieved by thermal treatment of beech wood with saturated water steam at temperature  $t_{III} = 137.5 \pm 2.5^\circ\text{C}$ , according to colorimetric classification of wood color changes (Cividini *et al.* 2007) belongs to categories of significant color changes.

By the visual inspection of the wood color on the sides of the beech blanks produced by sweeping and shortening of thermally treated lumber, as well as by measuring the color values at each CIE  $L^* a^* b^*$  color space coordinate, beech wood is uniformly throughout colored. The uniformity of coloring of the thermally modified wood throughout the volume makes it possible to use such treated wood for the production of slats for flooring, respectively other 3D processing of the massif without worrying about uneven coloring of wood along its cross-section between surface and center. The above-mentioned facts extend the possibilities of using beech wood with new color shades in the building-joinery, construction-artistic and designing area.

The evaluation of color changes in thermally treated beech wood according to the color space parameters CIE  $L^* C^* h^\circ$  shows, that by the increase in the temperature of saturated water steam in the technological process, the lightness  $L^*$  decreases significantly and the chroma  $C^*$  increases slightly. The decrease in the lightness of beech wood achieved by the individual thermal modes  $\Delta L^*$  and the increase in chroma  $\Delta C^*$  of the beechwood achieved by each mode at the temperature of the saturated water steam is shown in Figure 4.


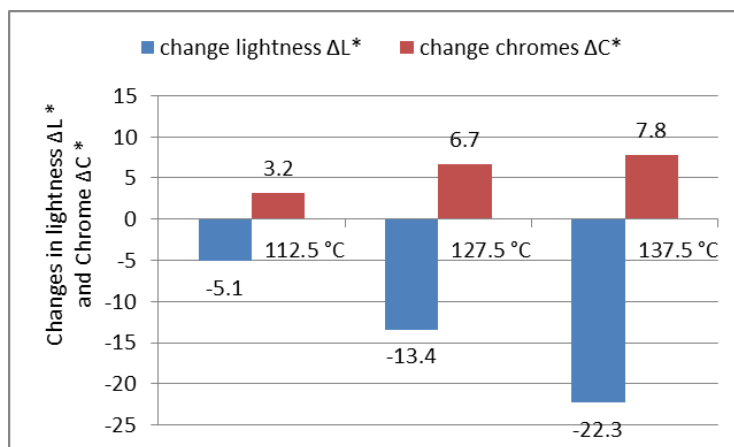


Figure 4. Dependence of lightness changes  $\Delta L^*$  and chroma  $\Delta C^*$  on temperature of saturated water steam in technological process.



The decrease in the lightness of beech wood with the increase in the temperature of the saturated water steam in the thermal treatment process is in line with the knowledges of wood darkening in technological processes such as wood steaming declared in the works: (Tolvaj *et al.* 2009, 2010; Dzurenda, 2018 b, c), drying in warm humid air, respectively overheated water steam (Klement and Marko 2009; Dzurenda and Deliiski 2012; Baranski *et al.* 2017) or in thermal treatment of wood in thermo-wood production (Barcik *et al.* 2015, Pinchevskaya *et al.* 2019).

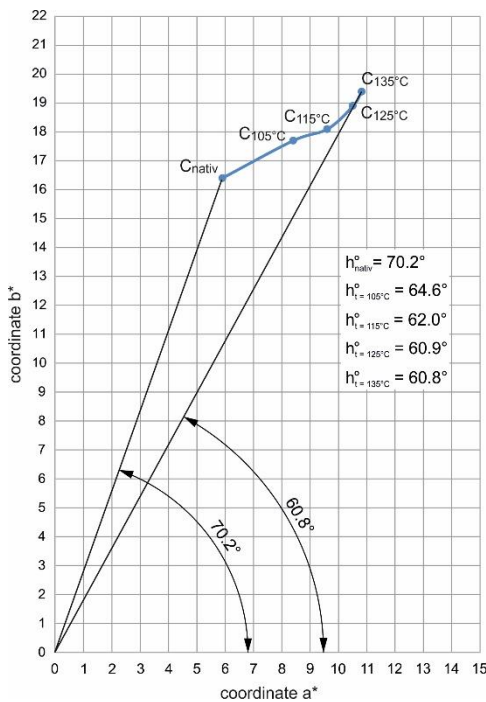

Changes in color saturation chroma  $C^*$  in the chromatic space of red color  $a^*$ , yellow color  $b^*$  and hue angle  $h^\circ$  of beech wood due to the increase of wood temperature in the technological process of beech wood color modification with saturated water steam are shown in Figure 5.

Figure 5. Color saturation changes in chroma  $C^*$  and hue angle  $h^\circ$  in chromatic space  $a^*$ ,  $b^*$ .

The increasing distance in chroma  $C^*$  on the color space  $a^*$ ,  $b^*$  (Figure 5.) from the center of the red color coordinates  $a^*$  and the yellow color  $b^*$  declares the saturation of the beech wood thermal treatment with saturated water steam. This knowledge is important for both wood processors and users of color-modified beech wood products with saturated water steam, because the richer colors of the interior objects are more acceptable for the human eye than the gray shades.

The dependence of total color difference changes  $\Delta E^*$  on wood temperature in technological process of color modification by saturated water steam of beech wood is shown in Figure 6.

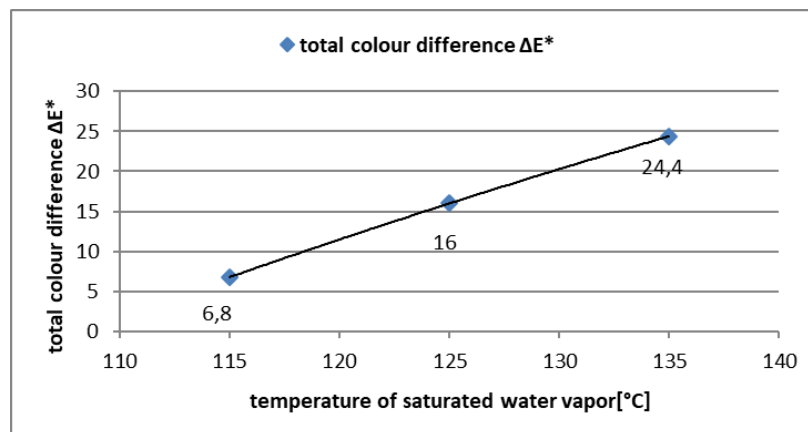


Figure 6. The dependence of total color difference changes  $\Delta E^*$  of beech wood on temperature of saturated water steam in technological process.

The total color differences of beech wood color  $\Delta E^*$  developed by water steam treatment with temperatures from the range 105 °C to 135 °C lies within the range of values:  $\Delta E^* = 6.8 \div 24.4$ . The mathematical dependence describing the color change of beech wood, shown in Figure 6., is in decisive extent determined by changes in the luminance coordinate of the thermally treated beech wood and in a lesser extent is determined with changes of red  $a^*$  and yellow  $b^*$  chromatic coordinates. According to the above-mentioned, dependence the significant changes in the brown-red color of beech wood occurs according to the categorization of the wood color changes magnitude in the thermal processes reported by Cividini *et al.* (2007), by the water steam temperature above  $t \geq 122$  °C.

According to the categorization of physico-mechanical and chemical changes of wood achieved by the technologies of thermal wood processing presented by the authors: Kollmann - Gote 1968; Trebula 1986, the beech wood color changes, achieved by any presented mode of the thermal treatment process, belong to the group of irreversible changes of wood. The irreversibility of color changes in beech wood is confirmed by differences in ATR-FTIR spectroscopy analyzes in the lignin-saccharide complex of untreated and treated wood (Geffert *et al.* (2017), Timar *et al.* (2016), Kučerová *et al.* (2016), as well as the presence of monosaccharides, organic acids and basic lignin units with guajacyl and syringyl structure in the condensate from thermal treatment reported in: (Bučko 1995; Dzurenda and Deliiski 2000; Kačík 2001; Laurova *et al.* 2004; Kačíková and Kačík 2011; Samešova *et al.* 2018).

The heat necessary for the implementation of technological process of beech wood color modification is provided by the intake of saturated steam to the autoclave from the steam boiler. APDZ 240 pressure autoclave heat balance for each beech wood color modification mode of thickness  $h = 40$  mm with moisture content  $w \approx 56\%$  and initial wood temperature  $t_d \approx 15$  °C for autoclave capacity  $V_D = 16$  m<sup>3</sup>, shows the Table 5.

Table 5 Heat consumption balance for thermal process of color modification of beech wood of  $h = 40$  mm in APDZ 240

Name of the heat consumption item	Symbol	Mode I.		Mode II.		Mode III.	
		MJ	[%]	MJ	[%]	MJ	[%]
Heating colour homogenised wood	$Q_{hw}$	3 867.2	70.7	4 860.2	72.6	5 323.9	73.2
Heating the autoclave's construction material	$Q_{hf}$	540.0	9.9	540.0	8.1	540.0	7.4
Heating the autoclave's insulation	$Q_{hil}$	82.6	1.5	101.7	1.5	110.4	1.5
Heat losses of the pressure autoclave	$Q_{he}$	64.9	1.2	85.5	1.3	101.6	1.4
Heat losses from extracted steam	$Q_{hfv}$	54.9	1.1	54.9	0.8	54.9	0.8
Heat losses from extracted condensate	$Q_{hfw}$	855.8	15.6	1 049.8	15.7	1 141.6	15.7
Normative $Q_{ha}$ for heat consumption	$\Sigma$	341.6 MJ·m-3		418.2 MJ·m-3		454.5 MJ·m-3	

The heat consumption expressed in the form of saturated water steam consumption of the pressure autoclave APDZ 240 for individual modes of wood color modification per 1 m<sup>3</sup> of beech wood with thickness  $h = 40$  mm is shown in Table 6.

Table 6 The consumption of saturated water steam of the pressure autoclave APDZ 240 for individual modes of wood color modification per 1 m<sup>3</sup> of beech wood with thickness  $h = 40$  mm

Mode of color modification	Saturated steam consumption in kg/m <sup>3</sup>
Mode I.	155.3
Mode II.	190.1
Mode III.	206.5

The heat consumption of thermally colored beech wood per 1 m<sup>3</sup> depending on the temperature of saturated steam in the technological process is:  $Q_{ha} = 341.6 - 454.5$  MJ/m<sup>3</sup>. A positive feature of the above-mentioned technology of thermal modification of wood color is the fact, that from 70.7% to 73.2% of the intake heat from saturated water steam, as shown in Table 5., is used to heat wood to the required technological temperature.

The technological process of color modification of beech wood with saturated water steam is a typical discontinuous process characterized by uneven heat consumption during the technological process. From the analysis of heat consumption of the technological process follows that the highest heat consumption is at the beginning of the technological process at the time  $\tau_0 \approx 1.5$  hours, when the heat of condensing water steam is used for heating of modified wood and heating the autoclave. Subsequently, the heat of condensing saturated steam is used to cover the losses of the heat in autoclave. In the second stage of the technological process  $\tau_2$ , steam is not fed into the autoclave and the losses of heat in autoclave is covered by the heat from the isochoric cooling of the saturated steam contained in the autoclave and also by the heat from the cooling of the autoclave construction material. Figure 5 shows the course of saturated water steam consumption at the temperature of  $t = 137.5 \pm 2.5$  °C for mode III of the thermal modification of beech wood color with thickness  $h = 40$  mm.

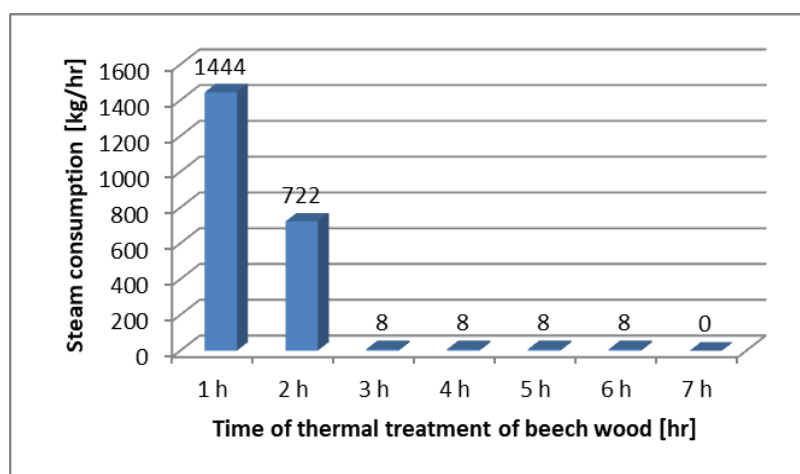


Figure. 5. The consumption of saturated water steam during the thermal modification of beech wood with thickness  $h = 40$  mm by the mode III. in autoclave APDZ 240

## 4. Conclusions

In this article are presented the changes of beech wood obtained in the targeted process of color modification with saturated water steam with temperatures  $t_I = 105 \pm 2.5^\circ\text{C}$  for  $\tau = 6$  hours (mode I.),  $t_{II} = 127.5 \pm 2.5^\circ\text{C}$  for  $\tau = 6.5$  hours (mode II.),  $t_{III} = 137.5 \pm 2.5^\circ\text{C}$  for  $\tau = 7$  hours (mode III.) and there are also characteristics of the technological process in terms of heat consumption and saturated water steam. These changes of beech wood were analyzed on the basis of targeted experimental work.

- the density of dry beech wood has been reduced due to the thermal modification during mode I. from  $\Delta\rho_0 = -1.74\%$  to  $\rho_0 = 671.8 \text{ kg.m}^{-3}$ , with mode II. increased from  $\Delta\rho_0 = +1.21\%$  to  $\rho_0 = 691.9 \text{ kg.m}^{-3}$  and with mode III. increased from  $\Delta\rho_0 = +3.05\%$  to  $\rho_0 = 705.0 \text{ kg.m}^{-3}$ .
- wet beech wood by thermal process of mode I. changes acidity from  $\text{pH} = 5.2$  to  $\text{pH} = 4.5$  with mode II. to  $\text{pH} = 4.0$  and with mode III. to  $\text{pH} = 3.7$ .
- the beech wood color changes from a light white-gray color with a yellow tinge to colors from brown-pink-yellow to brown-red hues of brown. With increasing temperature of saturated water steam which realize the process, the brightness of beech wood decreases and the wood stay dark. The color shade of thermally treated wood during mode I in the CIE-L\* a\* b\* color space is identified by the coordinate values:  $L_I^* = 71.5 \pm 2.1$ ;  $a_I^* = 11.1 \pm 1.7$ ;  $b_I^* = 21.5 \pm 1.5$ , in mode II. with coordinates:  $L_{II}^* = 63.2 \pm 2.4$ ;  $a_{II}^* = 14.9 \pm 2.1$ ;  $b_{II}^* = 23.3 \pm 1.7$  in mode III. with coordinates:  $L_{III}^* = 54.3 \pm 2.4$ ;  $a_{III}^* = 15.6 \pm 1.9$ ;  $b_{III}^* = 24.1 \pm 1.6$ .
- the range of total color differences  $\Delta E^*$  of the thermally modified beech wood by the individual modes is in the range of  $\Delta E^* = 6.4 - 24.4$  so its in terms of the magnitude categorization of the color changes reported by Cividini *et al.* (2007), beech thermally modified wood belongs to the category of visible and large color changes.
- heat consumption per  $1\text{m}^3$  of thermal modification of beech wood color in pressure autoclave APDZ 240 for mode I. is  $Q_{ha} = 341.6 \text{ MJ.m}^{-3}$ , for mode II. is  $Q_{ha} = 418.2 \text{ MJ.m}^{-3}$  and for mode III. is  $Q_{ha} = 454.5 \text{ MJ.m}^{-3}$ .

## Acknowledgment

This experimental research was prepared within the grant project: APVV-17-0456 “Termická modifikácia dreva sýtou vodnou parou za účelom cielenej a stabilnej zmeny farby drevnej hmoty” as the result of work of author and the considerable assistance of the APVV agency.

## References

Babiak, M., Kubovský, I., Mamoňová, M. (2004). Farebný priestor vybraných domácich drevín. In: *Interaction of wood with various Forms of Energy*. Technická univerzita Zvolen, pp. 113 – 117.

- Barański, J., Klement, I., Vilkovská, T., Konopka, A. (2017). High Temperature Drying Process of Beech Wood (*Fagus sylvatica* L.) with Different Zones of Sapwood and Red False Heartwood. In: *BioResources* 12(1), 1861-1870. doi:10.15376/biores.12.1.1761-1870.
- Barcik, Š., Gašparík, M., Razumov, E.Y. (2015). Effect of thermal modification on the colour changes of oak wood. In: *Wood Research*. 60 (3): pp. 385-396.
- Blažej, A., Šutý, L., Košík, M., Krkoška, P. and Golis, E. (1975). *Chémia dreva*. ALFA, Bratislava. 221 p.
- Bučko, J. (1995). *Hydrolyzné procesy*. Zvolen: Vydavateľstvo TU Zvolen, 116 p.
- Cividini, R., Travan, L., Allegratti, O.(2007). White beech: A tricky problem in drying process. In: *International Scientific Conference on Hardwood processing*. September 24-25-26, 2007 Quebec City, Canada.
- Čudinov, B. S. and Stepanov, V. L. (1968): Phasenzusammensetzung der Wassers in gefrorenem Holz. In: *Holztechnologie*, 9(1): 14-18 p.
- Dzurenda, L., Deliiski, N. (2010): Tepelné procesy v technológiách spracovania dreva. Zvolen: Vydavateľstvo TU vo Zvolene, 274 p.
- Dzurenda L., Orlowski K. (2011): The effect of thermal modification of ash wood on granularity and homogeneity of sawdust in the sawing process on a sash gang saw PRW 15-M in view of its technological usefulness. In: *Drewno*. [54] 186: pp. 27-37
- Dzurenda L., Deliiski N. (2012): Drying of beech timber in chamberdrying kilns by regimes preserving the original colour of wood. In: *Acta Facultatis xylogologiae Zvolen* [54] 1: pp. 33 – 42
- Dzurenda L. (2013): Modification of wood colour of *Fagus Sylvatica* L to a brown-pink shade caused by thermal treatment. In: *Wood research* [58] 3: pp. 475-482
- Dzurenda, L. (2014). Sfarbenie bukového dreva v procese termickej úpravy sýtou vodnou parou. In: *Acta facultatis xylogologiae Zvolen*, 56 (1): pp. 13 – 22.
- Dzurenda, L. (2016): Numeric Model of the Normative Consumption of Heat for the Colour Homogenisation of Wood in Pressure Autoclaves. In: *AIP Conference Processing*. 1745, 020008-1–020008-7; (2016), doi: 10.1063/1.4953702
- Dzurenda, L. (2018a). The Shades of Color of *Quercus robur* L. Wood Obtained through the Processes of Thermal Treatment with Saturated Water Vapor. In: *BioResouces* 13(1), pp. 1525 - 1533; doi: 10.1063/biores 13.1.1525-1533
- Dzurenda, L. (2018b). Hues of *Acer platanoides* L. resulting from processes of thermal treatment with saturated steam. In: *Drewno* 61(202): pp. 165-176.
- Dzurenda, L. (2018c). Colour modification of *Robinia pseudoacacia* L. during the processes of heat treatment with saturated water steam In: *Acta Facultatis Xylogologiae* 60(1): pp. 61-70.
- Dzurenda, L., Dudiak, M. (2019). The effect of the time and temperature of saturated water steam on the acidity and wood colour in the process of thermal modification of silver birch wood colour. In: *Wood technology & product design, Proceedings*. vol. IV. pp. 290-298. ISBN 978-608-4723-03-5.
- Fengel, D. and Wegener, G.(1989). *Wood: Chemistry, Ultrastructure, Reactions*; Walter de Gruyter: Berlin.

- Geffert, A., Geffertová, J. and Dudiak, M. (2019). Direct Method of Measuring the pH Value of Wood. In: *Forests* 10(10), 852; doi:10.3390/f10100852
- Geffert A., Výbohová E., Geffertová J. (2017) Characterization of the changes of colour and some wood components on the surface of steamed beech wood. In: *Acta facultatis xylologiae Zvolen*, [59] 1: pp. 49 – 57. doi: 10.17423/afx.2017.59.1.05
- Irlle, M. (2012). pH and why you need to know it. In: *Wood Based Panels International*. Available online: <http://www.wbpionline.com/features/ph-and-why-you-need-to-know-it/> (accessed on 20 August 2012)
- Kačík, F. (2001). Tvorba a chemické zloženie hydrolyzáto v systéme drevo-voda-teplo. Zvolen: TU Zvolen, 75 p.
- Kačíková, D., Kačík, F. (2011). Chemické a mechanické zmeny dreva pri termickej úprave Technická univerzita vo Zvolene, Zvolen, 71 p.
- Klement, I., Marko, P. (2009): Colour changes of beech wood (*Fagus sylvatica* L.) during high temperature drying process. In: *Wood research* 54 (3): pp. 45-54.
- Kollmann, F., Gote, W.A. (1968). Principles of Wood Sciences and Technology, Vol. 1. Solid Wood, Springer Verlag: Berlin – Heidelberg - New York, 592 p.
- Kučerová V., Lagaňa R., Výbohová E., Hýrošová T. (2016): The effect of chemical changes during heat treatment on the color and mechanical properties of fir wood. In: *BioResources*. [11] 4: pp. 9079-9094
- Kurjatko, S., et al. (2010) Parametre kvality dreva určujúce jeho finálne použitie. Technická univerzita vo Zvolene, Zvolen, 352 p.
- Laurova, M., Mamonova, M., Kučerova, V. (2004). Proces parciálnej hydrolyzy bukového dreva (*Fagus sylvatica* L.) parením a varením. Zvolen: TU Zvolen. 58 p.
- Lawniczak, M. (1995). Zarys hydrotermicznej i plastycznej obróbki drewna. Czesc I. – Warzenie i parzenie drewna. Poznan, 149 p.
- Makovíny, I. (2010). Úžitkové vlastnosti a použitie rôznych druhov dreva. Zvolen: Technická univerzita Zvolen, 104 p.
- Meints, T., Teischinger, A., Stingl, R. and Hassmann C. (2017). Wood colour of central European wood species: CIELAB characterisation and colour intensification. In: *Eur. J. Wood Prod.*, 75: pp. 499-509. doi 10.1007/s00107-016-1108-0.
- Melcer, I., Melcerová, A., Solár, R., Kačík, F. (1989). Chemizmus hydrotermickej úpravy listnatých drevín. Zvolen : Vysoká škola lesnícka a drevárska, 2/1989, 76 p.
- Molnar, S., Tolvaj, L. (2002): Colour homogenisation of different wood species by steaming. In: *Interaction of wood with various Forms of Energy*. Technical university in Zvolen, pp. 119–122.
- Nikolov, S., Rajchev, A., Deliiski, N. (1980). Proparvane na drvesinata. Sofia: Zemizdat, 174 p.
- Pinchevska, O., Sedliačik, J., Horbachova, O., Spirochkin, A., Rohovskyi, I. (2019). Properties of hornbeam (*Carpinus betulus*) wood thermally treated under different conditions. In: *Acta Facultatis Xylologiae Zvolen* 61(2): 25-39. doi: 10.17423/afx.2019.61.2.03.
- Požgaj, A., Chovanec, D., Kurjatko, S and Babiak M. (1997). “Štruktúra a vlastnosti dreva [Wood Structure and Properties]”. Príroda, Bratislava, 485 p.
- Prňakovič, L., Dzurenda, L. 2015. Combustion characteristics of fallen fall leaves from ornamental trees in city and forest parks. In: *BioResources*, 10(3): 5563-5572. DOI: 10.15376/biores.10.3.5563-5572.

- Samešová, D., Dzurenda, L., Jurkovič, P. (2018): Kontaminácia kondenzátu produktmi hydrolýzy a extrakcie v termickom procese farebnej modifikácie roztrúsenopórovitých listnatých drevín. In: *Trieskové a beztrieskové obrábanie dreva*, (2018), 11(1): pp. 235–239. ISSN 2453-904X
- Sanderman, W. and Rothkamm, M. (1959). The determination of pH values of woods and their practical importance. In: *Holz Roh- Werkstoff*, 17: pp. 433-441.
- Sergovskij, P. S., Rasev, A. I. (1987). *Gidrotermičeskaja obrabotka i konservirovanije drevesiny*. Lesnaja promyšlennost, Moskva, 360 p.
- Solár, R. (2004). *Chémia dreva*, Technická universita vo Zvolene, Zvolen. 102 p.
- Sundqvist, B., Karlsson, O., and Westremark, U. (2006). Determination of formic-acid and acid concentrations formed during hydrothermal treatment of birch wood and its relation to color, strength and hardness. In: *Wood Sci Technol* 40(7): pp. 549-561.
- Timar, M. C., Varodi, A. M., Hacibektasoglu, M., Campean, M. (2016): Color and FTIR analysis of chemical changes in beech wood (*Fagus sylvatica* L.) after light steaming and heat treatment in two different environments. In: *BioResources*, 11(4): pp. 8325-8343. doi: 10.15376/biores.11.4.8325-8343.
- Tolvaj, L., Nemeth, R., Varga, D., Molnar, S. (2009). Colour homogenisation of beech wood by steam treatment. In: *Drewno*. 52 (181): pp. 5-17.
- Tolvaj, L., Molnar, S., Nemeth, R., and Varga, D. (2010). Color modification of black locust depending on the steaming parameters. In: *Wood Research* 55(2), pp. 81-88.
- Trebula, P. (1996). *Sušenie a hydrotermická úprava dreva*. Zvolen: TU Zvolen, 255 p.
- Zevenhoven, M. 2001. *Ash-forming matter in biomass fuels*. Åbo/Turku: Faculty of Chemical Engineering, Akademi University. 88 p. ISBN 952-12-0813-9. 1